

## FUNGAL DEGRADATION OF CELLULOSIC MATERIALS USED AS SUPPORT FOR CULTURAL HERITAGE

Andrea C. MALLO<sup>1,5\*</sup>, Daniela S. NITIU<sup>1,6</sup>,  
Lorena A. ELÍADES<sup>2,6</sup>, Mario C. N. SAPARRAT<sup>2,3,4,6</sup>.

<sup>1</sup>Cátedra de Palinología, Facultad de Ciencias Naturales y Museo, Universidad Nacional de La Plata. Calle 64 N° 3 CP 1900. La Plata, Buenos Aires, Argentina.

<sup>2</sup>Instituto de Botánica Carlos Spegazzini, Facultad de Ciencias Naturales y Museo, Universidad Nacional de La Plata. Calle 51 N° 477 CP 1900. La Plata, Buenos Aires, Argentina.

<sup>3</sup>Instituto de Fisiología Vegetal, Facultad de Ciencias Agrarias y Forestales, Universidad Nacional de La Plata. Diag. 113 esq. 61 CP 1900. La Plata, Buenos Aires, Argentina.

<sup>4</sup>Cátedra de Microbiología Agrícola, Facultad de Ciencias Agrarias y Forestales, Universidad Nacional de La Plata. Av. 60 CP 1900. La Plata, Buenos Aires, Argentina

<sup>5</sup>Comisión de Investigaciones Científicas de la Provincia de Buenos Aires, (CIC, PBA) Argentina.

<sup>6</sup>Consejo Nacional de Ciencia y Tecnología (CONICET), Argentina.

### Abstract

*A great part of the cultural heritage of humanity available in museums and libraries is stored in paper. However, this main support used from early civilization times is a biomaterial susceptible to deterioration by fungal transformation. Two fungal phenomena, cellulose degradation and synthesis of secondary metabolites, are responsible for paper deterioration. Thus, the understanding of fungal deterioration pathways is key to improve the durability of the cultural heritage in paper and develop new and adequate sustainable strategies of restoration. This review gives an approach about the current knowledge of cellulose transformation by fungi associated with paper and the mechanisms involved. Since several metabolites derived from fungi growing on paper, such as pigments, can deteriorate invaluable cultural heritage, knowledge on these metabolites is also fundamental to improve conservation strategies of historical documents.*

**Keywords:** Biodegradation; Cellulolysis; Fungi; Pigments; Dyestuff; Cellulosic support, Preservation.

### Introduction

Since ancient times, paper has been one of the most used materials to record human knowledge. Although the use of electronic copies is currently widely spread [1], most people still use and value printed materials. Therefore, preserving and maintaining printed materials is crucial for librarians and specialists in libraries and information centers [2]. Biodegradation and biodeterioration of paper-made materials is a worldwide problem that causes great damage to unique manuscripts and books stored in libraries (Fig. 1).

The basic component of paper is cellulose; however, other constituents like starch, sugar, other carbohydrates and lignin are present [3]. Thus, paper is susceptible to a wide range of biological agents, including fungi, which have a remarkable capacity of dissolving cellulose as

\* Corresponding author: malloa2001@yahoo.com.ar

it provides a satisfactory medium for mold growth [4]. On the other hand, library environments, particularly old ones, provide microorganisms with nutritional requirements in the form of old papers and paper glues. In addition, the geographical situation and weather condition influence the diversity and content of fungi in confined environments [5]. Another important aspect of the microbiological contamination by fungi in libraries and archives is related to the health of workers since some species are also potentially pathogenic, causing allergy and toxic effects [2].



**Fig. 1.** Biodeterioration and biodegradation effects on library material stored in a building affected by flood: different materials affected by the colonization of fungi.

Fungi deteriorate paper used as support for cultural heritage as a result of their metabolic activity upon both cellulose and non-cellulosic additives such as binders, filling, adhesives and sizing agents [3]. Indeed, they are the most commonly found agents of degradation and they can be distinguish according to their capacity to degrade the various constituents of paper into fungi with cellulolytic activity and those able to degrade adhesives and/or additive compounds [6].

The biodegradation of paper by cellulolytic fungi involves two main processes: cellulose decomposition or production of fungal colored metabolites. The aim of this review is to give an approach about the current knowledge of cellulose transformation by fungi associated with paper and their role in the esthetic degradation.

#### ***Fungal features and their effect on biodegradation***

Fungi are a distinctive group of chemoorganotrophic eukaryotes that have a characteristic chitin cell wall and are phylogenetically circumscribed [7]. This group, with a total number of species estimated at around 1.5 million, can be classified into different groups based on phylogenetic, morphological, ecological and/or reproductive features [8, 9]. They are ubiquitous and able to colonize several substrata in terrestrial and freshwater habitats (less so in marine ones) since they present a wide range of adaptations to different environments. They play important ecological roles as saprotrophs, mutualistic symbionts, or parasites. They feed by absorption rather than by ingestion. Several fungal groups have an array of hydrolytic and oxidative exoenzymes that depolymerize the complex organic substrates on which they grow, followed by the absorption of the solubilized breakdown products; however, some of them can only use simple soluble substances such as sugars. Therefore, the ability to decompose carbon sources of increasing complexity has been associated with the taxonomic disposition of fungi [10]. While basal fungi according to the classification system from Hibbett et al. [7] which are widely considered to have a ruderal behaviour, are restricted to sugars and the simpler carbon compounds (thus called sugar fungi), the phyla Ascomycota and Basidiomycota include many representatives with the outstanding capacity of cellulose and lignin decomposition. Although most fungi are obligate aerobes, there are some facultative and obligate anaerobes such as different yeasts and those that live in the rumen of herbivores (e.g. rumen fungi), respectively.


Other parameters, such as air movement (since it can act as an additional source of spores), temperature, moisture, pH, and light, also govern fungal colonization, growth and

degradation of a substrate. In this sense, fungi are active on a substrate (e.g. in their saprotrophic role) when the environmental conditions are appropriate, i.e. when temperatures are around 25°C to 30°C, when water availability is high (relative humidity around 70-75% or higher), and when the bioreceptivity of the substrate and its physico-chemical properties are compatible with the demands of the fungi associated. Relative humidity and temperature have been reported to have a strong influence on the colonization and activity of a broad spectrum of fungi. When these factors are not appropriate, fungi decrease their degradative ability and can initiate reproductive processes, differentiate other somatic structures such as resting structures, or eventually die. If the conditions become favorable again, fungal growth will begin from the existing spores or other structures available in the substrate. However, some fungi can live under stressful conditions by using several mechanisms that allow functionality under such conditions (e.g. xerotolerant fungi).

During their life cycle, fungi can differentiate non-vegetative structures, which have distinctive features according to the taxonomic group to which they belong and are of systematic diagnosis. These structures may be involved in either sexual (i.e. nuclear fusion and meiosis) or asexual (i.e. purely mitotic nuclear division) reproduction. The sexual processes take place by the fusion of gametes (which characterize aquatic fungal groups and are associated with the presence of flagella) or gametic nuclei. They can also be associated with the differentiation of either macro - or microscopic sporophores (or fruiting bodies), which bear spores and show characteristic shapes, or with the direct generation of spores on undifferentiated structures as hyphae. Additionally, other propagules, which are typically microscopic, such as small spores produced in high numbers, can be asexually produced by fungi. These facilitate the conquest of new habitats and their substrates, and can be originated within a structure called sporangium (endogenous spores or sporangiospores) or not (exogenous spores called conidia). Also, several types of exogenous spores can be identified according to the type of ontogeny involved as well as to their features in the spore wall such as thickening and/or pigmentation. The morphology and structure of fungal spores show great variability, from unicellular to multicellular, branched or unbranched or sometimes spirally coiled, thin- or thick-walled with hyaline or pigmented walls, dry or sticky, smooth or ornamented by mucilaginous extensions, spines, folds or reticulations (Fig. 2).

Fungi are critical in the recycling of organic matter through the decomposition and the transformation of litter, wood and other residues available from plant productivity in several ecosystems as well as those from the domestic organic waste [11]. Fungi also have other beneficial effects because, for example, many species of mushrooms, morels and truffles are edible and provide a food source for humans and animals. In addition, many of them are a source for the industrial production of enzymes (including cellulases, amylases, proteases, lipases, and pectinases) and metabolites such as antibiotics, alkaloids and organic acids. Also, selected yeasts (*Saccharomyces* sp.) are the starting material for baking and brewing, and representatives of the genus *Penicillium* are used for the preparation of blue-type cheese. Besides, some fungal inoculants are used to promote plant growth. However, fungi can also have detrimental effects, causing diseases in plants of economic importance, and inducing animal and human diseases. They also attack and spoil all kinds of foodstuff, various objects like lumber and cloth, and other materials associated with buildings.

A critical aspect of fungal infection is related to the conservation of documents of heritage patrimony, which can be used by fungi as substrate and/or as a dispersion vehicle. Fungi play a considerable role in the damage of cultural heritage of paper-based and artworks of organic nature stored in museums and libraries. They can colonize these objects and deteriorate them by mechanical and chemical processes.

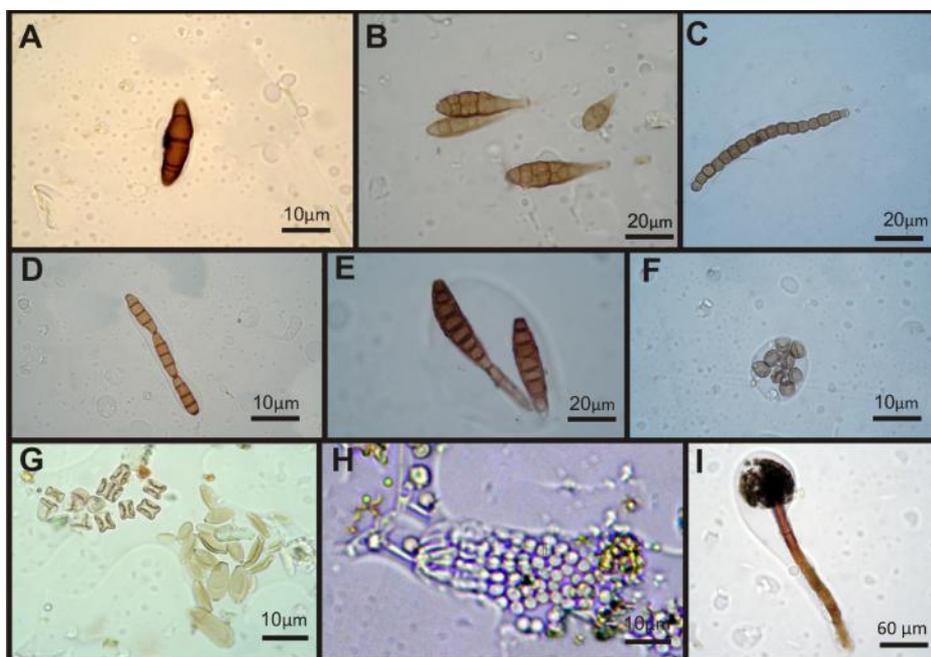

**Fig. 2.** Fungal sporal types recorded from indoor air: A- *Leptosphaeria*, B- *Alternaria*, C- *Torula*, D- Ascospores, E- *Stemphylium*, F- Myxomycota, G- *Cladosporium* and *Geothrichum*, H- *Aspergillus/ Penicillium*, I- *Mucor*.

#### ***Fungi associated with biodegradation in several paper documents***

In collections of cultural heritage as well as in libraries, paper and its derivatives are the dominant organic materials. In this environment, fungi play the most important role in biodegradation [25, 26]. Although bacteria can also degraded paper, fungi require less moisture to develop in the dry conditions that normally exist in libraries, archives or museums, being this kind of environment more favorable for the growth of fungi than bacteria [25].

Fungi causing biodegradation in paper come mainly from the air, accumulated dust and supports, being species of slow growth as well as xerophilic ones of the genera *Aspergillus*, *Paecilomyces*, *Chrysosporium*, *Penicillium* and *Cladosporium* belonging to the phylum Ascomycota [27]. Fungi colonize paper either by penetrating the microfibril matrix or growing superficially [13] to sustain their growth and reproduction as well as to be a vector/support for the dispersal of fungal propagules [28]. In addition, the hyphae of these cellulolytic fungi growing in the support exert a mechanical effect and generate a larger accessible microenvironment for the colonization and biofouling of non-cellulolytic microorganisms such as mucoraceous fungi [29] and several bacteria that form a biofilm [30]. This sequential process is promoted by the extracellular availability of a set of soluble organic products generated by cellulolytic fungi and by a higher retention of humidity in the attacked support.

Also, handling mold-contaminated paper objects can constitute a serious health risk, because many of these fungi can be pathogenic/toxicogenic, even when they are already dead [31, 32]. Besides, these microorganisms are widely recognized as allergenic triggers implicated in serious respiratory diseases [29]. Many fungi available in spore state in the air at high concentrations, such as those of the genus *Cladosporium*, can cause allergic respiratory diseases when inhaled [34, 12].

Table 1 summarizes the current knowledge of cellulose transformation by fungi associated with paper-made material of cultural heritage.

Table 1. Some fungi reported as biodeteriorating agents associated to several paper documents.


Substrate/source of isola	Taxa*	Observations	Reference
Laid-paper	<i>Cladosporium cladosporioides</i> <sup>a</sup>	The most recurrent species.	Mesquita et al. 2009 [12]
	<i>Cladosporium</i> <sup>a</sup> , and <i>Penicillium</i> <sup>a</sup> ,	The most frequent genera.	Mesquita et al. 2009 [12]
Laid-paper	<i>Chromelosporium carneum</i> <sup>a</sup> and <i>Toxicocladosporium irritans</i> <sup>a</sup> and	Less common species	Mesquita et al. 2009 [12]
Wood-pulp paper	<i>Aspergillus versicolor</i> <sup>a</sup> , <i>C. carneum</i> <sup>a</sup> , and <i>Penicillium chrysogenum</i> <sup>a</sup>	The most frequent species.	Mesquita et al. 2009 [12]
Wood-pulp paper	<i>Chaetomium globosum</i> <sup>a</sup>	The less common	Mesquita et al. 2009 [12]
Wood-pulp paper	<i>Phlebiopsis gigantea</i> <sup>b</sup>	The data available are confusing	Mesquita et al. 2009 [12]
Laid-paper	<i>Alternaria alternata</i> <sup>a</sup> and <i>Toxicocladosporium</i> <sup>a</sup>		Mesquita et al. 2009 [12]
1920 etching	<i>Taeniolella (Torula) sp.</i> <sup>a</sup>	Degradation associated to the presence of adhesives	Szczepanowska and Cavaliere, 2012 [13]
1958 etching	<i>Chaetomium sp.</i> <sup>a</sup>	Fungal degradation as a result of hurricane Katrina (2005)	Szczepanowska and Cavaliere, 2012 [13]
17 <sup>th</sup> century paper	<i>Aspergillus sclerotiorum</i> , <i>Cladosporium sp.</i> <sup>a</sup> and <i>Torula sp.</i> <sup>a</sup>		
A mold patch in a book		Material is of great heritage value from the "Coronado" archive, available in Centre of Documentation and Scientific-technic Information of the Universidad Central "Marta Abreu" de Las Villas, Cuba.	Szczepanowska and Cavaliere, 2012 [13] Carrazana-García et al 2014 [14]
Maps	<i>Aspergillus ssp.</i> <sup>a</sup> and <i>Penicillium ssp.</i> <sup>a</sup>	Map Library of National Archive of the Republic of Cuba.	Molina Veloso and Borrego Alonso (2014) [15]
Indoor air in an archive and one wood-pulp sample	<i>Aspergillus fumigatus</i> <sup>a</sup> , <i>Epicoccum nigrum</i> <sup>a</sup>	This fungus was the most frequent in indoor air.	Mesquita et al. 2009 [12]
Registry book of councils from the Santa Cruz Monastery (Coimbra)		Material was dated between the century 13 <sup>th</sup> to 14 <sup>th</sup>	Mesquita et al. 2009 [12]
In foxing spots in Leonardo da Vinci's self-portrait	<i>Eurotium halophilicum</i> <sup>a</sup>	By SEM analyses	Piñar et al. 2015 [15]
Leonardo da Vinci's self-portrait	Lichenized Ascomycota or <i>Acremonium sp.</i> <sup>a</sup> as the most dominant taxa	This is variable depending on the sampling techniques used (Swabs samples vs membrane filters, respectively).	Piñar et al. 2015 [16]
A degraded paper of a 16 <sup>th</sup> -century book	<i>Aspergillus versicolor</i> <sup>a</sup> , <i>Aspergillus nidulans</i> <sup>a</sup> , <i>Botryotinia fuckeliana</i> <sup>a</sup> , <i>Cladosporium cladosporioides</i> <sup>a</sup> , <i>Debaryomyces hansenii</i> <sup>a</sup> , <i>Epicoccum nigrum</i> <sup>a</sup> , <i>Penicillium pinophilum</i> <sup>a</sup> , <i>Rhizopus arrhizus</i> <sup>c</sup>	By DNA-fingerprinting and phylogenetic analysis using fragments of paper.	Michaelsen et al. 2006 [17]
Deteriorated 19 <sup>th</sup> -century photographs, books and maps	<i>Alternaria sp.</i> , <i>Aspergillus niger</i> , <i>Aspergillus flavus</i> , <i>Cladosporium sp.</i> , <i>Fusarium sp.</i> , <i>Penicillium sp.</i> , <i>Scopulariopsis sp.</i>	The genus <i>Aspergillus</i> was predominant and colonies of the other taxa where isolated in different substrata <i>Scopulariopsis sp.</i> and <i>Fusarium sp.</i> were able to adhere to paper, using it as the sole carbon source. Also were able to attach to aged paper after incubation, develop a biofilm and cause a generalized attack on the paper	Lavin et al., 2016 [18]
Paper (laid-paper, wood pulp paper) and cellulose textiles (cotton, linen)	<i>Alternaria sp.</i> , <i>Aspergillus clavatus</i> , <i>A. flavus</i> ; <i>A. glaucus</i> , <i>A. terreus</i> , <i>A. repens</i> , <i>A. ruber</i> , <i>A. fumigatus</i> , <i>A. ochraceus</i> , <i>A. nidulans</i> , <i>Aspergillus</i> sect. <i>Niger</i> , <i>Botrytis cinerea</i> , <i>Chaetomium globosus</i> , <i>C. elatum</i> , <i>C. indicum</i> , <i>Eurotium astelodami</i> ,	Data based in more than 20 studies carried out in Austrian museums.	Sterfingler 2010 [19]

	<i>Fusarium</i> sp., <i>Mucor</i> sp., <i>Paecilomyces variotii</i> , <i>Penicillium chrysogenum</i> , <i>P. funiculosum</i> , <i>P. purpurogenum</i> , <i>P. rubrum</i> , <i>P. variable</i> , <i>P. spinulosum</i> , <i>P. fellutatum</i> , <i>P. frequentans</i> , <i>P. citrinum</i> , <i>Pichia guilliermondi</i> , <i>Ryzopus oryzae</i> , <i>Stacybothrys charatarum</i> , <i>Toxicocladosporium irritans</i> , <i>Trichoderma harzianum</i> , <i>T. viride</i> , <i>Stemphium</i> sp., <i>Ulocladium</i> sp.		
Air, surfaces of books and shelves	<i>Acremonium</i> , <i>Alternaria</i> , <i>Aspergillus niger</i> , <i>Aspergillus</i> sp., <i>Aureobasidium</i> , <i>Botrytis</i> , <i>Chaetomium</i> , <i>Cladosporium</i> , <i>Curvularia</i> , <i>Deschlera</i> , <i>Epicoccum</i> , <i>Fusarium</i> , <i>Geotrichum</i> , <i>Mucor</i> , <i>Neurospora</i> , <i>Penicillium</i> , <i>Phoma</i> , <i>Rhizopus</i> , <i>Rhodotorula</i> , <i>Scopulariopsis</i> , <i>Syncephalastrum</i> , <i>Trichoderma</i> , <i>Trichosporon</i> .	Data obtained on Library materials of the Isfahan University of Medical Sciences	Chadeganipour <i>et al</i> , 2013 [5]
Paper arts, paper paintings, manuscripts	<i>Aspergillus</i> , <i>Alternaria</i> , <i>Cephalosporium</i> , <i>Cladosporium</i> , <i>Fusarium oxysporum</i> , <i>Curvularia lunata</i> , <i>Chaetomium</i> , <i>Mycelia sterilia</i> , <i>Mucor</i> , <i>Penicillium</i> , <i>Phoma</i> , <i>Stachybothrys</i> , <i>Trichoderma</i>	Dominating in all sites. Many of the taxa produce various coloured superficial stains causing chromatic and aesthetic of paintings. Cellulolytic activity of <i>Alternaria alternata</i> , <i>Aspergillus niger</i> , <i>Fusarium oxysporum</i> , <i>Phoma</i> and <i>Trichoderma</i> were studied at different pH and temperature.	Shrivastava, 2015 [4]
Textile heritage objects	<i>Aspergillus penicillioides</i>	The biodiversity analysis with the PCR-DGGE technique revealed differences in both the number and biodiversity of fungal genotypes.	Lech <i>et al.</i> , 2015 [20]
Environmental air and chemically treated books from the Brazilian Public Library Biblioteca de Maginhos, FIOCRUZ Rio de Janeiro	<i>Aspergillus versicolor</i> , <i>Eurotium chevalieri</i> (teleomorph of <i>A. chevalieri</i> )	Radiosensitivity tests were applied in fungi isolated in paper and wood. <i>A. versicolor</i> was inactivated with doses 20 kGy.. <i>E. chevalieri</i> was inactivated with doses 14,5 kGy.	Da Silva <i>et al</i> , 2006 [21]
Glided wood of two altars present in Espiritu Santo church – Santa Ursula Altar and Nosa Senhora da Boa Morte Altar (Évora, Portugal)	<i>Cladosporium</i> (4 strains), <i>Mucor</i> (1 strain), <i>Penicillium</i> (2 strains).	The predominant microbial agents were filamentous fungi as the main agents for alteration of wood. Cellulolytic and xylanolytic enzymes were detected.	Rosado <i>et al</i> 2015 [22]
Maps on textile and paper conserved in the Archivo Nacional de Cuba	<i>Aspergillus flavus</i> , <i>A. niger</i> , <i>A. oryzae</i> , <i>A. caespitosus</i> , <i>A. ornatus</i> , <i>Penicillium citrinum</i> , <i>P. fellutanum</i> , <i>P. waksmanii</i>	<i>A. caespitosus</i> and <i>A. ornatus</i> were potent degradative agents of cellulose, starch and gellatine. The authors of this paper studied the enzymatic activity and biodeteriorative capacity of the isolated strains.	Molina Veloso and Borrego Alonso, 2014 [15]
Dust samples from archival bindings and shelves of a repository of the Sala Alessandrina in the Archive of the State in Rome	<i>Cladosporium</i> , <i>Penicillium</i> , <i>Aspergillus</i> , <i>Chaetomium</i> , <i>Alternaria</i>	<i>Cladosporium</i> predominated in winter samples. <i>Penicillium</i> predominated in summer samples. The authors stand up that dust creates a microenvironment and trophic resource for the microorganisms.	Maggi <i>et al</i> , 2000 [23]
Paper artworks	<i>Alternaria solani</i> , <i>Penicillium notatum</i> , <i>Fusarium oxysporum</i> , <i>Chaetomium globosum</i>	Describes a method for the rapid production of fungal stains on paper and the stain removal and stain prevention.	Szczepanowska & Lovett, 1992 [24]

\*a, phylum Ascomycota; b, phylum Basidiomycota; c, Subphylum Mucoromycotina.

### *Fungi and their ability to cause structural damage in paper*

The saprotrophic abilities of fungi cause the disintegration of the organic matter since they use cellulose as a source of energy when they colonize paper. Because the structure of cellulose is organized in both amorphous and crystalline regions, most of the fungi that grow on it are cellulolytic. The process of biodegradation by fungi involves both enzymatic and non-enzymatic mechanisms (Fig. 3). It is believed that cellulose is depolymerized through three main types of extracellular hydrolases: 1) endoglucanases, 2) exoglucanases, including cellodextrinases and cellobiohydrolases and 3)  $\beta$ -glucosidases [35]. Among these enzymes, endoglucanases are key in the process because they increase notoriously the number of (new) reducing and non-reducing extremes (including chain ends and oligosaccharides). Although endoglucanases are active on amorphous regions of cellulose, other proteins, such as swollenin, whose primary action is to enhance access to the hemicelluloses fraction, play a role in amorphogenesis (see below) [35, 36]. This increases the cellulose surface area by the slippage of cellulose microfibrils and thereby opens up the fibrillar matrix (creating new surfaces within the cellulose matrix) and provides the catalytic enzymes with enhanced access to the glycosidic linkages within the sugar polymers as well as reactivity of cellulose.

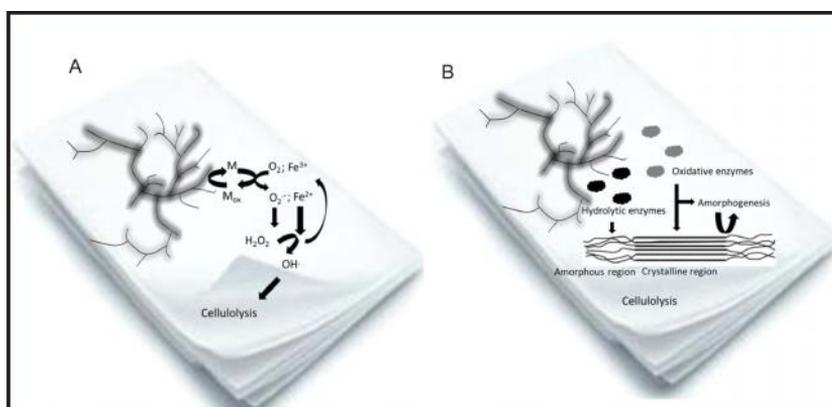

**Fig. 3.** Fungal degradation of cellulose. A. Schematic overview (not to scale) of non-enzymatic mechanisms involving the production of hydroxyl radicals, which disrupt cellulose, through oxygen activation in the presence of a fungal metabolite (M) and  $\text{Fe}^{3+}$  ions. Based on Gómez Toribio et al. [55] and Baldrian and Valásková [56]. B. Simplified scheme of the current view (not to scale) on the degradation of cellulose through extracellular hydrolases, which are active on amorphous parts of cellulose, and extracellular oxidoreductases, which play a role in amorphogenesis of the highly crystalline regions of cellulose and are implicated in the oxidative cleavage of the polymer. Based on Dimarogona et al. [38] and Cragg et al. [39].

In 1985, *M.P. Coughlan* [37] coined the term ‘amorphogenesis’ to suggest a possible mechanism by which the dispersion, swelling or delamination of cellulosic substrate occurred, resulting in a reduction in the degree of fibrillar aggregation and/or crystallinity, and the creation of a larger accessible surface by increasing the reactive internal surface. Consequently, amorphogenesis enhances the reactivity of the fibrous cellulosic substrates by increasing the amount of cellulose directly accessible to the enzymes [38]. Different amorphogenesis-inducing agents, including non-hydrolytic proteins such as fungal expansion-like proteins, loosenin and swollenin, have been proposed to participate in the disruption and weakening of the plant cell wall or cellulosic substrates [36]. Although considerable progress has been made to elucidate the way of action of these proteins in amorphogenesis through the disruption of hydrogen bonding between adjacent sugar chains, weakening paper and reducing its crystallinity index, the mechanism is still not well understood [35, 36]. Additionally, the knowledge on the enzyme systems used by fungi to degrade cellulose has changed dramatically in the last years [39]. There is recent evidence that different fungi degrade cellulose by means of oxidative enzymes that act complementarily to the long-known hydrolytic cellulase system [39].

In addition, non-enzymatic mechanisms can act in conjunction with processes via enzymes. Such non-enzymatic processes are associated with the activity of some Basidiomycota fungi such as the brown-rot ones. These fungi generate small molecular mass oxidants that randomly attack the substrate through quinone redox cycling and glycopeptide-based Fenton reaction [40].

Fungi that colonize damaged paper are mostly cellulolytic organisms, bearers of an array of depolymerizing enzymes; however, the microbiota associated with this substrate can also include fungi with different saprotrophic behaviours such as non-cellulolytic ones. For example, representatives of Mucorales that belong to sugar fungi are unable to use complex carbohydrates because they lack the battery of extracellular enzymes. However, they can play a role as opportunists on deteriorated paper. If spores are available and conditions to germinate are appropriate, they develop typical colonies using soluble C compounds, which are easily assimilable and derived from the cellulose depolymerization caused by the activity of extracellular enzyme systems that have been secreted by cellulolytic fungi.

In addition to cellulose and its monomers, paper can harbor other important sources of carbon like fillers, sizings or dust, which can be rich in proteins and sugars or by scavenging CO<sub>2</sub>, combined nitrogen, and carbon-rich gases from the atmosphere. Then, under stressful conditions, fungi can develop feeding from these alternative substrata [41]. In addition, the survival strategy of the fungi that deteriorate paper under these conditions might also include the use of alternative endogenous C sources like lipids available in spores. All these limitations can lead to inconspicuous mycelial development on paper, which is associated with the production of fungal secondary metabolites rather than biomass accumulation [42].

#### ***Fungal ability to deteriorate paper esthetically***

##### *Foxing*

Some natural changes in the coloration of paper can result from the physico-chemical transformations of their components (such as type-lignin aromatic compounds) due to time. Another cause of the colorimetric alterations in paper is due to fungal growth. The staining activity by fungi is considered derived from the synthesis of pigments and/or from the Maillard reaction of by-products of the fungal metabolism such as organic acids, oligosaccharides and proteic compounds that react together chemically with the material under specific conditions (at a low water activity and high temperature). This latter process forms brown products and oxidative reactions, probably resulting in melanoidin production and the consequent formation of foxing-type spots [16, 43].

Foxing spots generally appear on the paper as stains of reddish-brown, brown or yellowish color, small dimensions, and sharp or irregular edges, frequently showing fluorescence if excited with UV light [44, 45]. Foxing spots have been observed in different kinds of paper since the 16<sup>th</sup> Century. Although the mechanisms involved in the formation of these spots have been studied since 1930-1935 [45], the results are controversial and still not conclusive. A theory about the origin of foxing spots postulates the action of abiotic processes, but the nature of foxing is still under discussion. Recently, *E. Ardelean and N. Melniciuc-Puică* [44] reported the following summary of the possible causes that generate the appearance of foxing spots: 1. Direct metal oxidation produces a distinct dark center and the migration of the soluble degradation products from the metallic center causes the surrounding discoloration. 2. Microorganism contamination is mostly airborne in origin and produces irregular yellow-brown patches. 3. Metals and fungi produce acid in the cellulose, which causes deleterious effects on papers (the foxing phenomenon has been related to a strong oxidation of the cellulose chain [46]). 4. Relative humidity increases the chemical reactivity of auto-oxidation, causing cellulosic discoloration in the wet/dry interface on the paper's surface.

Weather foxing can appear due either to iron oxidation or to the influence of microorganisms; future studies are necessary to research if the induction of fungal siderophores (molecules secreted by the fungi under iron limitation to chelate this metal) and their interaction with iron within the paper matrix are involved in the developing of the foxing phenomenon. On the other hand, the presence of foxing spots has been also related to condensation reactions between products of cellulose oxidation with nitrogen-containing compounds, according to the

formation of humic-type aromatic polymers (browning theory [47]). Anyway, this hypothetical mechanism can not be ruled out because, among other things, these processes can vary depending on the external conditions and the original composition of the paper. As can be seen, additional studies are required to identify the processes and conditions that contribute to the development of foxing in paper, which is probably a plethora of abiotic and biotic processes.

#### *Fungal pigments/dyestuff*


Many fungi that paper degradation synthesize different pigments/dyestuff, such as lipophilic ones (e.g. carotenoids), hydrophilic ones (e.g. anthraquinones) and those which are only soluble in alkaline solutions like melanins, which are an assemblage of a dark polymers highly recalcitrant [48]. These secondary metabolites, which may cause extensive color changes in the substrate, can play an array of functional roles in the fungal biology. This mechanism can work as a protector agent against environmental stress (including photo-oxidation) or against other organisms (antimicrobial action) [49, 50], or as an intermediate related to enzyme cofactors [51]. In this sense, there are fungi growing on paper that increase their pigmentation by the establishment of stressful conditions such as those generated by the irradiation with gamma radiation as control treatment on paper, as reported by *S.C. Pavon Flores* [52]. Despite this negative effect, it is necessary to advance in the assessment of the performance of this type of treatment for cleaning heritage documents. *C. Llorente et al.* [53] reported data about the nature of a dark pigment (1,8-dihydroxynaphthalene (DHN)-melanin) in agar-cultures of *Cladosporium cladosporioides* and mentioned that the pigmentation of its colonies was increased under the chemical stress imposed by certain fungicides. Therefore, the excretion of pigmented polymeric substances by this type of dematiaceous fungus and other relatives growing on cellulosic supports is a serious problem in the management of the biodeterioration of material of cultural heritage. Since this fungus frequently deteriorates paper and is an inhabitant in the indoor air of libraries and museums, it is a priority to study the process of melanization in this fungus and its relationship with environmental conditions.

The process of production and accumulation of pigments in deteriorated paper takes place in structures on which fungi are able to develop depending on the taxonomic group to which they belong and to their ecophysiology. Pigments can occur in spores, fruiting structures and mycelium as well as in resistance somatic structures such as the sclerotia. This can be variable depending on the physiological state of the fungus, which produce differential effects on the substrate [54].

Figure 4 (A-D) shows the colonization of abaca paper by *Chaetomium globosum* LPSC 259, the organization of fibrillary matrix of the attacked paper and the pigmented reproductive structures differentiated by the fungus (perithecium and spores). Although *H. Szczepanowska* and *A.R. Cavaliere* [13] suggested that the staining of several papers deteriorated by *Cladosporium* sp. and *Chaetomium* sp. was confined to the fungal elements, several studies have shown that the fungal pigments can also be secreted into the substrate and so spread far away from the origin source. *H.J. Choi et al.* [55] reported the production of 2-methylresorcinol, a diffusible pigment which appears to be an active antimicrobial principle, by the *Helicosporium* sp. isolate (Ascomycota). Besides, pyomelanin (alkaptomelanin), a water-soluble brown pigment, has been reported to be synthesized by different fungi under certain culture conditions (e.g. in the presence of aromatic amino acids as phenylalanine and tyrosine that are likely necessary for its synthesis). This type of pigment exhibits protecting properties against different kinds of stress such as those generated by reactive oxygen intermediates [56, 57].

There are species of the genus *Aspergillus*, including *A. fumigatus*, a typical fungal representative that deteriorates paper, that are able to produce pyomelanin. *A. fumigatus* is able to produce several melanins, including a DHN-type melanin insoluble in water, which is predominantly present in conidia, and an alternative melanin synthesized extracellularly, accumulated in the hyphae and excreted into the medium, generating darkened mycelia by the deposition of the pigment on the surface of hyphae [58-60]. On the other hand, *A. Michaelsen et al.* [17] postulated that the pinkish to purple-colored spots frequently found in sheets of 16<sup>th</sup>-century books are caused by migration of purple exudates of the cellulolytic fungi *Aspergillus*

*versicolor* and *A. nidulans* through the pages with a felted consistency. Therefore, fungal staining can be a relevant factor that deteriorates paper and affects the choice of adequate strategies of restoration. This is compatible with results reported in experiments with bleaching agents to reduce discoloration and stains [12].

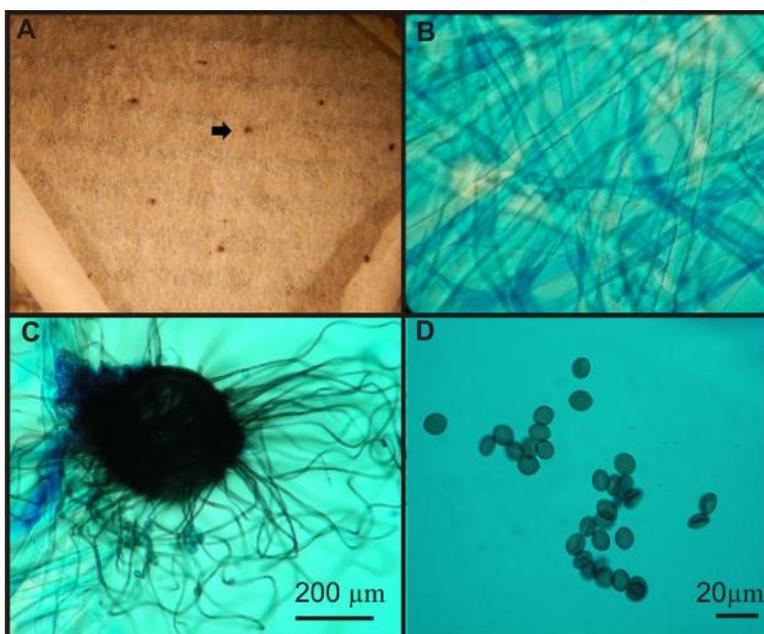

**Fig. 4.** A-D. In-vitro degradation of abaca paper by *Chaetomium globosum* LPSC 259 after 1 month of incubation. A. General view of a sample of paper probe incubated axenically in the presence of sexual spores from the fungus under a 95 % moisture environment, showing several dark spots (arrow) that correspond to pigmented perithecia differentiated by the fungus. B. Fibrillar matrix of fungi-deteriorated paper showing cotton blue-stained hyphae. C. Detail of a dark perithecium with unbranched radiating hairs, associated in its basis with a mass of cotton blue-stained hyphae that are bound to the deteriorated paper. D. Mass of free pigmented ascospores generated into asci differentiated in the inside of the perithecium.

## Conclusions

The cleaning and the control of environmental conditions where cultural heritage is stored as well as the monitoring of the indoor air quality are key procedures in the prevention of biodegradation. However, it is clear that strategies against fungal degradation of paper must still be improved to minimize the attack and staining of paper. As described in this review, the degradation of cellulose by fungi causes both detrimental effects on paper-made documents and generates various intermediate by-products, which affect the physico-chemical and nutritional quality of the deteriorated material. This precondition facilitates the colonization by non-cellulolytic fungi that can secrete other problematic metabolites. The knowledge of the biology of these fungi belonging to different ecophysiological groups is relevant for practical aspects of preservation and restoration of deteriorated and degraded paper. However, there are no concluding data about the key mechanisms and the environmental factors that control paper deterioration and degradation. In addition, the nature of chromophores synthesized by fungi when they grow on paper is unknown. Therefore, more investigations are still necessary to develop effective and sustainable processes to decrease the impact of fungal degradation on the cultural heritage.

## Acknowledgments

The present study was financially supported by the Consejo Nacional de Investigaciones Científicas y Técnicas (CONICET) PIP 112-201101-00087, PIP 112-201101- 00391. Agencia Foncyt PICT 2013-0418. This research was partially supported by Agencia Nacional de Promoción Científica y Tecnológica (PICT 2015-1620 to MCNS), Argentina. & Proyecto de Incentivos a la Investigación (N11/781) of the Facultad de Ciencias Naturales y Museo (FCNyM), Argentina. The authors would like to thanks to the reviewers for their timely suggestions. Lic. Andrea C. Mallo belongs to the Comisión de Investigaciones Científicas de la Provincia de Buenos Aires (CIC. PBA) and Dr. Lorena Elíades, Dr. Daniela S. Nitiu and Dr. Mario Saparrat are researchers from Consejo Nacional de Investigaciones Científicas y Tecnológicas (CONICET). Argentina.

## References

- [1] O.M., Bankole, *A review of biological deterioration of library materials and possible control strategies in the tropics*, **Library Review**, **59**(6), 2010, pp. 414-42.
- [2] M. Breitenbach, *The spectrum of fungal allergy*, **International Archives of Allergy and Immunology**, **145**(1), 2008, pp. 58-86.
- [3] N. Bhardwaj, I.K. Bhatnagar, *Microbial deterioration of paper paintings*, **Biodeterioration of Materials**, **2**, 2002, pp. 132-135.
- [4] S. Shrivastava, *Biodeterioration of art objects on paper and their conservation*, **Research Journal of Recent Sciences**, **4**(IVC-2015), pp. 42-46.
- [5] M. Chadeganipour, R. Ojaghi, H. Rafiei, M. Afshar, S.T. Hashemi, *Bio-Deterioration of library material: study of fungi threatening printed materials or libraries in Isfahan University of Medical Sciences in 2011*, **Jundishapur Journal of Microbiology**, **6**(2), 2013, pp. 127 – 131.
- [6] G. Pasquariello, P. Valenti, O. Maggi, A.M. Persiani, *Biodeterioration processes in relation to cultural heritage materials*, **Plant Biology for Cultural Heritage: Biodeterioration and Conservation** (Edited by G. Caneva, M.P. Nugari, M.P. Salvadori), Getty Conservation Institute, 2009, pp. 108 – 113.
- [7] D.S. Hibbett, M. Binder, J.F. Bischoff, M. Blackwell, P.F. Cannon, O.E. Eriksson, S. Huhndorf, T. James, P.M. Kirk, R. Lücking, H.T. Thorsten Lumbsch, F. Lutzoni, P.B. Matheny, D.J. McLaughlin, M.J. Powell, S. Redhead, C.L. Schoch, J.W. Spatafora, J.A. Stalpers, R. Vilgalys, M.C. Aime, A. Aptroot, R. Bauer, D. Begerow, G.L. Benny, L.A. Castelbury, P. W. Crous, Y.C. Dai, W. Gamsi, D.M. Geiser, G.W. Griffith, C. Gueidan , D.L. Hawksworth, G. Hestmark, K. Hosaka, R.A. Humber, K.D. Hyde, J.E. Ironside, U. Kõljalg , C.P. Kurtzman, K.H. Larsson, R. Lichtward, J. Longcore, J. Miadliskowska, A. Miller, J.M. Moncalvo, S. Mozley-Standrige, F. Oberlinker, E. Parmasto, V. Reeb , J.D. Rogers, C. Roux, L. Ryvarden, J.P. Sampaio, A. Schüßler, J. Sugiyama, R.G. Thorn, L. Tibell, W.A. Untereiner, C. Walker, Z. Wang , A. Weir, M. Weiss, M.M. White, K. Winka, Y.J. YAO, N. Zhang, *A higher-level phylogenetic classification of the Fungi*, **Mycological Research**, **111**(5), 2007, pp. 509-547.
- [8] D.L. Hawksworth, *The magnitude of fungal diversity: the 1.5 million species estimate revisited*, **Mycological Research**, **105**(12), 2001, pp. 1422-1432.
- [9] P. M. Kirk, P.F., Cannon, J.C. David, **Ainsworth & Bisby's Dictionary of the Fungi 9<sup>th</sup> Edition**, Cabi Publishing, UK, 2001.
- [10] S.D. Garret, *Ecological groups of soil fungi: a survey of substrate relationships*, **The New Phytologist**, **50**(2), 1951, pp. 220 – 251.
- [11] M.C.N. Saparrat, A. Bárcena, P. Balatti, *Microorganismos del suelo y su participación en la formación de la materia orgánica: lignocelulólisis y mecanismos involucrados*, **Microbiología Agrícola. Un aporte de la investigación en Argentina**, 2nd Ed., Capítulo del Eje Temático: Materia Orgánica del Suelo, ISBN 978-987-1726-17-2.

- Universidad Nacional de Santiago del Estero, Magna Publicaciones (Tucumán), 2013, pp. 65-92.
- [12] N. Mesquita, A. Portugal, S. Videira, S. Rodriguez-Echeverri, A.M.L. Bandeira, M.J.A. Santos, H. Freitas, *Fungal diversity in ancient documents. A case study on the Archive of the University of Coimbra*, **International Biodeterioration & Biodegradation**, **63**(5), 2009, pp. 626-629.
- [13] H. Szczepanowska, A.R. Cavaliere, *Conserving our cultural heritage: The role of fungi in biodeterioration*, **Bioaerosols – Fungi, Bacteria, Mycotoxins in Indoor and Outdoor Environments and Human Health** (Edited by E. Johannng, P. R. Morey, P. L. Auger), Fungal Research Group, Albany, 2012, pp. 293-309.
- [14] D.I. Carrazana-García, D. González-Álvarez, E. Díaz-Álvarez, L. Mesa-Garriga, A. Banguela-Castillo, A. Chea-González, R. Cupull-Santana, *Aspergillus sclerotiorum: riesgo para la herencia cultural y la salud*, **Universitas Scientiarum**, **19**(3), 2014, pp. 323-332.
- [15] A. Molina Veloso, S.F. Borrego Alonso, *Caracterización de hongos aislados de mapas conservados en el Archivo Nacional de la República de Cuba*, **Ge-Conservación**, **6**, 2014, pp 35-44.
- [16] G. Piñar, H. Tafer, K. Sterflinger, F. Pinzari, *Amid the possible causes of a very famous foxing: molecular and microscopic insight into Leonardo da Vinci's self portrait*, **Environmental Microbiology Reports**, **7**(6), 2015 849-59.
- [17] A. Michaelsen, F. Pinzari, K. Ripka, W. Lubitz, G. Piñar, *Application of molecular techniques for identification of fungal communities colonizing paper material*, **International Biodeterioration and Biodegradation**, **58**(3-4), 2006, pp. 133-141.
- [18] P. Lavin, S. Gómez de Saravia, P. Guiamet, *Scopulariopsis sp. and Fusarium sp. in the documentary heritage: evaluation of their biodeterioration ability and antifungal effect of two essential oils*, **Microbial Ecology**, **71**(3), 2016, pp. 628-633.
- [19] K. Sterflinger, *Fungi: Their role in deterioration of cultural heritage*, **Fungal Biology Reviews**, **24**(1-2), 2010, pp. 47-55.
- [20] T. Lech, A. Ziembinska-Buczynska, N. Krupa, *Analysis of the microflora present on historical textiles with use of molecular techniques*, **International Journal of Conservation Science**, **6**(2), 2015, pp. 137-144.
- [21] M. Da Silva, A.M.L. Moraes, M.M Nishikawa, M.J.A. Gatti, M.A. Vallim de Alencar, L.E. Brandão, A. Nóbrega, *Inactivation of fungi from deteriorated paper material by radiation*, **International Biodeterioration and Biodegradation**, **57**(3), 2006, pp. 163-167.
- [22] T. Rosado, M. Silva, C. Pereira, J. Mirão, J. Schmalder-Ripcke, V. Sugareva, P. Gebhardt, R. Winkler, O. Kniemeyer, T. Heinekamp, A.A. Brakhage, *Production of pyomelanin, a second type of melanin, via the tyrosine degradation pathway in Aspergillus fumigates*, **Applied Environmental Microbiology**, **75**(2), 2009 pp. 493-503.
- [23] O. Maggi, A.M. Persiani, F. Gallo, P. Valenti, G. Pasquariello, M.C. Sclocchi, M. Scorrano, *Airborne fungal spores in dust present in archives: proposal for a detection method, new for archival materials*, **Aerobiologia**, **16**(3-4), 2000, pp. 429-434.
- [24] H. Szczepanowska, C.M. Lovett, *A study of the removal and prevention of fungal stains on paper*, **Journal of the American Institute of Conservation**, **31**(2), 1992, pp. 147-160.
- [25] S. Sequeira, E.J. Cabrita, M.F. Macedo, *Antifungal on paper conservation: An overview*, **International Biodeterioration and Biodegradation**, **74**, 2012, pp. 67 - 85.
- [26] K. Sterflinger, G. Piñar, *Microbial deterioration of cultural heritage and works of arts - tilting at windmills? Applied Microbiology Biotechnology*, **97**(22), 2013, pp. 9637-9646.
- [27] F. Pinzari, M. Montanari, *Mould growth on library materials stored compactus-type shelving units, Sick Building Syndrome in Public Buildings and Workplaces* (Edited by S.A. Abdul-Wahab), Springer, Berlin, 2011, pp. 196-203.

- [28] F. Pinzari, G. Pasquariello, A. De Mico, *Biodeterioration of Paper: A SEM Study of Fungal Spoilage Reproduced Under Controlled Condition*, **Macromolecular Symposia**, **238**, 2006, pp. 57-66.
- [29] J.W. Spatafora, Y. Chang, G.L. Benny, K. Lazarus, M.E. Smith, M.L. Berbee, G. Bonito, N. Corradi, I. Grigoriev, A. Gryganskyi, T.Y. James, K. O'Donnell, R.W. Roberson, T.N. Taylor, J. Uehling, R. Vilgalys, M.M. White, J.E. Stajich, *A phylum-level phylogenetic classification of zygomycete fungi based on genome-scale data*, **Mycologia**, **108**(5), 2016, 1028-1046.
- [30] A.M. del Carmen Calvo, A. Docters, M.V. Miranda, M.C.N. Saparrat, *The Use of Gamma Radiation for the Treatment of Cultural Heritage in the Argentine National Atomic Energy Commission: Past, Present, and Future*, **Topics in Current Chemistry**, **375**(1), 2017, pp. 375-79.
- [31] J.W. Bennett, M. Klich, *Mycotoxins*, **Clinical Microbiology Reviews**, **16**(3), 2003, pp. 497-516.
- [32] A.C. Pinheiro, M.F. Macedo, V. Jurado, C. Sainz Jimenez, C. Viegas, J. Brandão, L. Rosado, *Mould and yeast identification in archival settings: Preliminary results on the use of traditional methods and molecular biology options in Portuguese archives*, **International Biodeterioration and Biodegradation**, **65**(4), 2011, pp. 619-627.
- [33] A.H. Khan, S.M. Karupppayil, *Fungal pollution of indoor environments and its management*, **Saudi Journal of Biological Sciences**, **19**(4), 2012, pp. 405-426.
- [34] M.E. Lacey, J.S. West, **The Air Spore**, Springer, Dordrecht, Netherlands, 2006.
- [35] I.C.A. Sandu, C. Luca, I. Sandu, *A study on the paintings cloth-supports ageing degradation*, **Revista de Chimie**, **50**(12), 1999, pp. 902-908.
- [36] K. Gourlay, J. Hu, V. Arantes, M. Andberg, M. Saloheimo, M. Penttilä, J. Saddler, *Swollenin aids in the amorphogenesis step during the enzymatic hydrolysis of pretreated biomass*, **Bioresource Technology**, **142**, 2013, pp. 498-503.
- [37] M.P. Coughlan, *The properties of fungal and bacterial cellulases with comment on their production and application. Biotechnology and genetic engineering reviews*, **Interscience**, **3**, 1985, pp. 37-109.
- [38] V. Arantes, J.K. Saddler, *Access to cellulose limits the efficiency of enzymatic hydrolysis: the role of amorphogenesis*, **Biotechnology for Biofuels**, **3**(4), 2010.
- [39] M. Dimarogona, E. Topakas, P. Cristakopoulos, *Cellulose degradation by oxidative enzymes*, **Computational and Structural Biotechnolgy Journal**, **2**, 2012, e201209015.
- [40] S.M. Cragg, G.C. Beckham, T.N. Bruce, T.D.H. Bugg, D.L. Distel, P. Dupree, A.G. Etxabe, B.S. Goodell, J. Jellison, J.E. McGeehan, S. J. McQueen-Mason, K. Schnorr, P.H. Walton, J.E. Watts, M. Zimme, *Lignocellulose degradation mechanisms across the Tree of Life*, **Current Opinion in Chemical Biology**, **29**, 2015, pp. 108-119.
- [41] M.I. Troncozo, R.P. Gómez, A.M. Arambarri, P.A. Balatti, A.M.M. Bucsinzsky, M.C.N. Saparrat, *Growth and oxidative enzymatic activity of in-vitro cultures of Ciliochorella buxifolia*, **Mycoscience**, **56**(1), 2015, pp. 58-65.
- [42] M.C. Pagano, P.P. Dhar, *Fungal pigments: An overview* (Chapter 13), **Fungal Biomolecules: Sources, Applications and Recent Developments** (eds V.K. Gupta, R.L. Mach and S. Sreenivasaprasad), John Wiley & Sons, Ltd, Chichester, UK., 2015, doi: 10.1002/9781118958308.
- [43] F. Gallo, **Il biodeterioramento di Libri e Documenti**. Centro di Studi per la Conservazione della Carta, ICCROM (International Centre for the Study of the Preservation and Restoration of the Cultural Property), Roma, 1992, pp. 128
- [44] E. Ardelean, N. Melniciuc-Puică, *Conservation of paper documents damaged by foxing*, **European Journal of Science and Theology**, **9**(2), 2013, pp. 117-124.
- [45] S.F. Ibrahim, D.M. Essa, F.M. Tera, *fast production of artificial mimic textile samples using uv/ozone treatment application in conservation and consolidation*, **International Journal of Conservation Science**, **6**(1), 2015, pp. 15-22.
- [46] Ch. Prajapati, **Conservation of Documents: Problems and Solutions: Policy Perspectives**, Mittal Publication, New Delhi, 2005.

- [47] M. Bicchieri, S. Ronconi, F.P. Romano, L. Pappalardo, M. Corsi, G. Cristoforetti, S. Legnaioli, V. Palleschi, A. Salvetti, E. Tognoni, *Study of foxing stains on paper by chemical methods, infrared spectroscopy, micro-X-ray fluorescence spectrometry and laser induced breakdown spectroscopy*, **Spectrochimica Acta, Part B - Atomic Spectroscopy**, **57**(7), 2002, pp. 1235-1249.
- [48] G. Guggenberger, *Humification and Mineralization in Soils*, **Microorganisms in Soils: Roles in Genesis and Functions** (Edited by F. Buscot and A. Varma), Springer, Berlin, 2005, pp. 85-106.
- [49] W. Noshuytta, E. Osman, M. Mansour, *An investigation of the biological fungicidal activity of some essential oils used as preservatives for a 19th century Egyptian coptic cellulosic manuscript*, **International Journal of Conservation Science**, **7**(1), 2016, pp. 41-56.
- [50] G.M. Simu, I.V. Ledeti, S.G. Muntean, A. Fulias, I.M. Citu, C. Soica, D. Onisei, G. Savoiu-Balint, I. Pinzaru, D. Ionescu, *Study of the Interaction of Some Pharmaceutical Compounds with Different Cellulosic Supports*, **Revista de Chimie**, **65**(6), 2014, pp. 664-670.
- [51] V.A. Toledo, E.M.E Franco, Y.S.M. Lopez, M. Troncozo, M.C.N. Saparrat, P.A. Balatti, *Melanins in fungi: Types, localization and putative biological roles*, **Physiological and Molecular Plant Pathology**, **99**, 2017, pp. 2-6.
- [52] S.C. Pavon Flores, *Gamma Radiation as Fungicide and Its Effects on Paper*, **Bulletin of the American Institute for Conservation of Historic and Artistic Works**, **16**(1), 1976, pp. 15-44.
- [53] C. Llorente, A. Bárcena, J. Vera Bahima, M.C.N Saparrat, A.M Arambarri, M.F. Rozas, M.V. Mirífico, P.A. Balatti, *Cladosporium cladosporioides LPSC 1088 produces the 1,8-dihydroxynaphthalene-melanin-like compound and carries a putative pks gene*, **Mycopathologia**, **174**(5-6), 2012, pp. 397-408.
- [54] F. Pinzari, *Microbial ecology of indoor environments: The ecological and applied aspects of microbial contamination in archives, libraries and conservation environments*, **Sick Building Syndrome in Public Buildings and Workplaces** (Edited by S.A. Abdul-Wahab), Springer, Berlin, 2011, pp. 153-168.
- [55] H.J. Choi, S.M. Lee, S.H. Kim, D.W. Kim, Y.W. Choi, W.H. Joo, *A novel Helicosporium isolate and its antimicrobial and cytotoxic pigment*, **Journal of Microbiology and Biotechnology**, **22**(9), 2012, pp. 1214-1217.
- [56] S. Keller, J. Macheleidt, K. Scherlach, J. Schmalzer-Ripcke, I.D. Jacobsen, T. Heinekamp, A.A. Brakhage, *Pyomelanin Formation in Aspergillus fumigatus Requires HmgX and the Transcriptional Activator HmgR but Is Dispensable for Virulence*, **PLOS ONE**, **6**(10), 2011, e26604.
- [57] R. Almeida-Paes, S. Frases, G. de Sousa Araújo, M.M. Evangelista de Oliveira, G.J. Gerfen, J.D. Nosanchuk, R.M. Zancopé-Oliveira, *Biosynthesis and functions of a melanoid pigment produced by species of the Sporothrix complex in the presence of L-Tyrosine*, **Applied and Environmental Microbiology**, **78**(24), 2012, pp. 8623-8630.
- [58] J. Schmalzer-Ripcke, V. Sugareva, P. Gebhardt, R. Winkler, O. Kniemeyer, T. Thorsten Heinekamp, A.A. Brakhage, *Production of Pyomelanin, a Second Type of Melanin, via the Tyrosine Degradation Pathway in Aspergillus fumigates*, **Applied and Environmental Microbiology**, **75**(2), 2009, pp. 493-503.
- [59] V. Gómez-Toribio, A.B. García- Martín, M.J. Martínez, F. Guillén, *Enhancing the production of hydroxyl radicals by Pleurotus eryngii via quinone redox cycling for pollutant removal*, **Applied Environmental Microbiology**, **75**(12), 2009, pp. 3954-62.
- [60] P. Baldrian, V. Valášková, *Degradation of cellulose by basidiomycetous fungi*, **FEMS Microbiology Review**, **32**(3), 2008, pp. 501-521.

---

Received: December 15, 2016

Accepted: November 25, 2017